

Strain mediated Filling Control nature of the Metal-Insulator Transition of VO₂ and electron correlation effects in nanostructured films

A. D'Elia^{a,*}, C. Grazioli^a, A. Cossaro^{a,b}, B.W. Li^c, C.W. Zou^c, S.J. Rezvani^{d,a}, N. Pinto^e,
A. Marcelli^{d,f,g}, M. Coreno^g

^a IOM-CNR, Laboratorio TASC, Basovizza SS-14, km 163.5, 34149 Trieste, Italy

^b Department of Chemical and Pharmaceutical Sciences, University of Trieste, via L. Giorgieri 1, Trieste, Italy

^c National Synchrotron Radiation Laboratory, University of Science and Technology of China, Hefei 230029, PR China

^d Istituto Nazionale di Fisica Nucleare, Laboratori Nazionali di Frascati, 00044 Frascati, Italy

^e Scuola di scienze e tecnologie, Sezione di Fisica, Università di Camerino, Via Madonna delle Carceri 9, 62032 Camerino, Italy

^f Rome International Centre for Material Science Superstripes, RICMASS, Via dei Sabelli 119A, 00185 Rome, Italy

^g ISM-CNR, Istituto Struttura della Materia, LD2 Unit, Basovizza Area Science Park, 34149 Trieste, Italy

ARTICLE INFO

Keywords:

Filling Control
Strained VO₂
Nanostructured Disordered VO₂
Screening parameter
Fermi level population control
Electron correlation

ABSTRACT

The Metal-Insulator transition (MIT) in VO₂ is characterized by the complex interplay among lattice, electronic and orbital degrees of freedom. In this contribution we investigated the strain-modulation of the orbital hierarchy and the influence over macroscopic properties of the metallic phase of VO₂ such as Fermi Level (FL) population and metallicity, i.e., the material ability to screen an electric field, by means of temperature-dependent X-ray Absorption Near Edge Structure (XANES) and Resonant Photoemission spectroscopy (ResPES). We demonstrate that the MIT in strained VO₂ is of the Filling Control type, hence it is generated by electron correlation effects. In addition, we show that the MIT in Nanostructured (NS) disordered VO₂, where the structural phase transition is quenched, is driven by electron correlation. Therefore a fine tuning of the correlation could lead to a precise control of the transition features.

1. Introduction

The ability to manipulate the charge carrier flow within a solid state material is at the basis of the modern electronics. There have been a vast investigations on such manipulations via the material dimension [1,2], surface-interface customization [3,4] and the structural strain application [5–7], however all compounds that intrinsically exhibit alternating itinerant-to-localized behaviour of the electrons result extremely appealing.

Among the different systems offering this possibility, such as perovskites, transition metal dichalcogenides and transition metal oxides [8–10] the VO₂ is one of the most studied.

VO₂ is a 3d¹ electron system, which undergoes a reversible Metal-Insulator Transition (MIT) coupled to a structural phase transition, going from a low temperature monoclinic insulator to a high temperature tetragonal (rutile) metal [11,12]. The near room temperature (~340 K in bulk) phase transition, is of paramount interest for a variety of applications, ranging from energy saving and smart windows [13] to

the emerging field of Mottronics [14,15].

The physical mechanism behind the insulating gap opening has been long debated. In literature, different models have been proposed to explain the VO₂ MIT: a structurally driven phase transition triggered by a Peierls instability [12], a pure electronic Mott-Hubbard phase transition [16] or a combination of both [17,18].

This long standing debate has been fuelled by the complex interplay between, lattice, orbital and electronic degrees of freedom, which modify the MIT features like transition temperature and width [5,7,19–28]. As a consequence a tremendous effort has been devoted to the disentangle of the multiple degrees of freedom that regulate the MIT [29–31], however the complete understanding and control over manipulation of the transition has not yet been achieved. Among the different methods developed to tune the MIT, the application of the epitaxial strain to VO₂ thin films emerged as one of the most effective ways to enhance the electron–electron interaction and, therefore, to customize the transition process [21,32–35]. However, complete disentanglement of electronic and structural degrees of freedom is not

* Corresponding author.

E-mail address: delia@iom.cnr.it (A. D'Elia).

achieved in strained samples where the local atomic configurations deeply affect the orbital ordering of the metallic phase at the Fermi Level (FL) [5,21,27].

We used X-ray Absorption Near Edge Structure (XANES) and Resonant Photoemission spectroscopy (ResPES), to clarify the role of the local arrangements around vanadium atoms and the electron correlation over the orbital hierarchy, metallicity and Fermi Level population in the conductive phase of vanadium dioxide. The use of these powerful spectroscopic techniques is necessary to concurrently probe multiple degrees of freedom, e.g. XANES is an atomically selective probe of the local order and of the different final states configurations which are crucial to understand the MIT features in VO_2 [36].

Our research shows that the MIT in strained VO_2 is of the Filling Control (FC) type and as a consequence is mainly driven by electron correlation effects [37]. This is confirmed by studying the extreme case of a Nanostructured (NS) disordered sample where the structural phase transition is quenched by disorder, i.e. electronic and structural degrees of freedom are disentangled. In this limiting case, concurrent spectroscopic-electronic transport measurements point out the pure electronic character of the transition, suggesting that the electron interaction is the key parameter to tune MIT features.

2. Experimental

Films of VO_2 having a thickness of 8, 16 and 32 nm were deposited on a clean substrate of TiO_2 (001) by the RF-plasma assisted Molecular Beam Epitaxy instrument working with a base pressure better than 4×10^{-9} mbar. These film were grown at the constant growth rate of 0.1 \AA/s and their thickness was controlled by monitoring the deposition time. The substrate has been kept at the temperature of 550°C during the deposition process. The interfacial cross-section has been investigated with the high-resolution scanning transmission electron microscope (STEM). High angle annular dark field (HAADF) STEM images were taken on a JEM ARM200F using a probe aberration corrector, while the diffraction pattern was acquired on a JEM 2100 TEM. Information and details of the epitaxial films preparation and characterization are reported elsewhere [21,38].

The NS VO_2 sample has been synthesized using a Pulsed Microplasma Cluster Source available at TASC laboratories [39]. The PMCS is a pulsed-cluster source driven by a pulsed electric discharge. In the present experiment, the PMCS was used with a vanadium cathode (6 mm diam. rod, purity 99.9%, EvoChem GmbH) in order to generate a supersonic beam seeded with vanadium oxide clusters. Homogeneously oxidized nanoparticles have been obtained using Ar (high purity Ar: 99.9995%, SIAD) as the carrier gas, mixed with a controlled quantity of oxygen ($\text{O}_2/\text{Ar} = 0.3\% \text{ mol}$) as described in [40]. The base pressure of the experimental chamber was 1×10^{-7} mbar, during the deposition process. The working parameters of the PMCS have been adjusted in order to maximize the deposition rate (delay between gas injection and discharge firing = 0.61 ms; discharge operating voltage 0.9 kV; discharge duration 60 μs ; pulsed-valve aperture driving signal duration time 210 μs ; pulse repetition rate 3 Hz; Ar- O_2 pressure feeding the Parker valve 60 bar).

The XANES and ResPES experiments have been performed at the ANCHOR end-station of the ALOISA beamline [41] at Elettra synchrotron radiation facility. Electrons were collected at normal emission by a PSP Vacuum 120 mm electron analyser with 2D delay line detector. The photon beam was linearly polarized in the scattering plane and impinging the sample at the magic angle (35° measured respect to the sample surface). Measurements were performed at constant pass energy ($E_p = 20 \text{ eV}$).

The XANES spectra have been acquired in Auger yield ($\text{O KL}_{23}\text{L}_{23} \sim 507 \text{ eV}$) in order to minimize the V L edges contribution [42,43].

Transport properties have been carried out at dark in a small furnace operating in vacuum ($P < 10^{-5}$ mbar). The sample temperature has been measured and controlled within 0.1 K by a thermocouple (type N)

connected to the temperature controller Eurotherm mod. 3216. The film temperature has been changed slowly, with a rate of $\sim 0.5 \div 1 \text{ K/min}$, in an uninterrupted cycle from room temperature (RT) up to about 400 K and then back to RT. The two co-planar contacts geometry has been chosen, considered the high RT resistance exhibited by all films, fixing two thin Cu wires onto the film surface by using silver paint. The film resistance has been measured by an electrometer Keithley 6517B operated in the V/I mode, applying a constant bias (0.5 V) and measuring the current flowing through the contacts. Each $R(T)$ value has been measured after stabilization of the temperature. For every T, at least 25 points of $R(T)$ values have been averaged to calculate the corresponding $\rho(T)$ mean value. For each film the measurement has been repeated several times under the same nominal conditions, all but the applied bias [44,45]. Current-voltage (I-V) characteristics have been detected at several fixed temperatures, by using a source-meter Keysight mod. B2912A.

3. Results and discussion

To recognize the multi-orbital character of the MIT it is necessary to understand how the local arrangement of the oxygen atoms around the vanadium atom determines the band structure of VO_2 . In the metallic phase of bulk vanadium dioxide, ligand atoms arrange according to a slightly distorted octahedral symmetry around the metal site with two nonequivalent V-O bond distances, namely equatorial and apical [5,21,34]. The octahedral crystal field splits the degenerate 3d manifold into 3 t_{2g} and 2 e_g levels. In addition, the small orthorhombic distortion separates the 3 t_{2g} levels in one singly degenerate a_{1g} and two e_g levels. The e_g and e_g orbitals hybridize with the O 2p, forming bonds of σ and π symmetry [12]. Their unoccupied levels are identified as π^* (e_g^* character) and σ^* (e_g character). The a_{1g} orbital, populated by unpaired 3d electrons, it is called $d_{||}$ [12]. In the conductive state, π^* and $d_{||}$ bands are slightly degenerate at the Fermi Level (FL).

In the insulating phase, the pairing of vanadium atoms increases the superposition of V 3d wave functions splitting the $d_{||}$ creating an antibonding empty $d_{||}^*$ band. Within the ligand octahedron, the V-V dimerization has the concomitant effect of moving off-centre the metal atom and increasing the superposition between e_g^* and oxygen wave functions. As a consequence the π^* band is upshifted in energy opening a gap. The antibonding $d_{||}^*$ is strictly related to the presence of unidimensional V-V dimer chains in the monoclinic insulating phase [46].

Changing the atomic distances in a controlled fashion, e.g. through the application of an epitaxial strain, affect both wave functions overlap and electron correlation and, as a consequence, the electronic structure of VO_2 . The lattice mismatch of VO_2 grown on TiO_2 (001) thin films results in an increase of the apical V-O distance, which reduces the superposition between oxygen and vanadium orbitals and therefore the 3d-2p hybridization [21,34]. The π^* orbital, which points toward other vanadium atoms and it is directed between the oxygen corners of the octahedron, is the most affected [5]. As a consequence, the decrease in V-O hybridization reduces the bonding-antibonding energy separation, hence the π^* orbital is shifted to lower energy. At variance, the $d_{||}^*$ shifts upwards since the strain reduces the inter-pair distance increasing the orbitals superposition within the unidimensional V-V chains. In synthesis, in the metallic phase, the strain reverses the $\pi^*-d_{||}^*$ hierarchy modifying the orbital population at the FL. In the insulating phase where the V-O hybridization is stronger, the $\pi^*-d_{||}^*$ splitting increases, with $d_{||}^*$ being at higher energy. Increasing the wave functions overlap also influences the electron correlation, which has been demonstrated to have a major effects on the MIT in VO_2/TiO_2 (001) thin films respect to the strain-induced structural rearrangement [5].

For the NS disordered sample the description of the electronic structure is complicated by the presence of multiple distorted phases coexisting within the same film. As demonstrated by a previous investigation, the

VO₂ NS sample synthesized by a PMCS is characterized by a local disorder [47]. The disordered nature of this NS VO₂ film point out that the role of the Peierls pairing mechanism that requires an ordered crystalline structure can be neglected, giving us the unique opportunity to study a VO₂ sample in which structural and electronic contributions to the phase transition are almost disentangled.

To confirm the quality of the samples and the resistive switching behaviour of VO₂ transport measurements were carried out on samples of 8, 16 and 32 nm of thickness as described in the experimental section in the cooling-heating uninterrupted cycle. The resistivity behaviour of these samples as a function of temperature is shown in Fig. 1a. The resistivity curves show the typical hysteresis observed in VO₂, while the transition temperature shifts with the film thickness from ~ 315 K in the 8 nm film to ~ 345 K in the 32 nm film in agreement with the relative VO₂ bulk transition temperature [11,48]. The decrease of the temperature can be directly correlated to the strain induced variation of the V-V/V-O distances and hence to the variation of the p-d hybridization and electron-electron interaction as will be discussed in details later on. The resistivity temperature coefficient derived as $-1/\rho(dp/dT)$ with a numeric derivative of the resistivity as function of the temperature, returns a transition width of the order of 15 K (see Fig. 1b), indicating a high degree of crystallinity in samples [28].

The differential conductivity, σ , of the 32 nm films calculated from the numeric derivative of the I-V measurements at 300 and 365 K is shown in Fig. 1c.

The differential conductivity versus the applied potential is a sensitive probe for the energy dependence of current carrying states in the material. In our measurements it is a qualitative representation of density of states (DOS) and available transition states. The voltage widths around the minimum is proportional to the insulating gap in the band structure. Thus, the voltage width reduction in the curve of the 32 nm thick film, increasing the temperature from 300 K to 365 K, points to a reduction of the insulating gap and thus to the transition to the metallic phase with an increase of the empty states. The decrease of the differential conductivity width starts as soon as the resistivity value in the split region of the curve of the resistivity vs. temperature decreases, confirming the hypothesised shift in the DOS and the change of the population of π^* , $d_{||}^*$ bands at the FL as a function of the temperature.

In order to correlate the MIT features with the orbital ordering across the phase transition, a series of temperature dependent XANES measurements have been performed. In vanadium oxides, V 3d and O 2p electrons strongly hybridize [24] hence measuring the O K edge XANES [42,48,49] it is possible to probe the π^* , $d_{||}^*$ and σ^* bands and, in general the empty bands with t_{2g} and e_g character.

Fig. 2 reports the XANES spectra of the VO₂ films. The 8, 16 and 32 nm films show intense and well-separated π^* and σ^* resonances at about 529.8 and 532.2 eV, respectively indicating an intense crystal field

contribution that indicates also the local order of these samples [42,49]. At variance, the $d_{||}^*$ band sets between 530.5 and 531 eV is not well resolved [32,48,49]. Across the MIT a slight increase of the intensity in the π^* energy region is observed (see Fig. 2 left panel) concurrent with a depletion of the valley between π^* and σ^* , which going from the high to low temperature phases is compatible with the collapse of the $d_{||}^*$ band at the FL.

On the other hand the nanostructured film characterized by a disordered nature does not well separate π^* and σ^* resonances [47,49,50]. This interpretation is also supported by the shift of the σ^* band toward a lower photon energy by ~ 1 eV respect to the crystalline samples. σ^* relative position respect to π^* is directly related to the 10Dq crystal field intensity [51] and therefore to the local structural order of the ligands arrangement. Nevertheless across the MIT, spectral changes are observed also in the t_{2g}^* energy region.

For strained samples, decreasing the thickness we observed an increase in the deepness of the $d_{||}^*$ valley across the MIT. This is compatible to a hierarchical modulations of the π^* and $d_{||}^*$ bands induced by the epitaxial growth [5,21].

To investigate the strain induced orbital hierarchy inversion, we investigated the differences among the XANES spectra between the insulating and the metallic phase.

The differences among XANES spectra are shown in the right panel of Fig. 2 and have been calculated as [34]:

$$I_{ins} - I_{met} \propto uDOS_{ins} - uDOS_{met} \quad (1)$$

where I_{ins} and I_{met} are the intensity of the XANES spectra of the insulating and the metallic phases and $uDOS_{ins}$ and $uDOS_{met}$ are the empty DOS, respectively. Using the Eq. (1) a negative contribution is expected in the spectral region where the metallic empty DOS is more intense. A turning point (TP) from negative to positive contribution is also expected where the metallic and the insulating empty DOS coincide. In our samples as the strain increases the positive contribution in the $h\nu$ range 530–531 eV grows with an asymmetry toward high photon energy. The negative contribution in the 528–529.7 eV decreases and the TP shifts toward lower photon energy. The latter is a fingerprint of the shrinking of the metal empty DOS with a simultaneous widening of the insulating empty DOS. They are expected to cross at a lower photon energy, in agreement with the qualitative band description of Fig. 2 and the strain dynamics of π^* - $d_{||}^*$ bands in insulating and metallic phases. The growing asymmetry in the positive contribution at 530–531 eV, is also in agreement with the strain-induced increase of the π^* and $d_{||}^*$ separation in the insulating phase. Furthermore, increasing the film strain, the negative contribution decreases which is a result of a highly occupied π^* band in the strained films.

Looking at the XANES spectra of the metallic phase, decreasing the

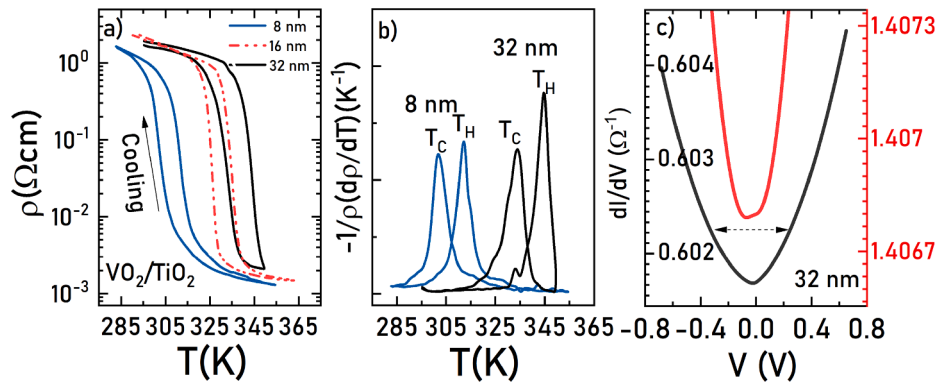


Fig. 1. The transport properties of the VO₂ thin films: a) the resistivity of 8, 16 and 32 nm thick film as a function of temperature in the heating-cooling cycle; b) the temperature coefficient of the resistivity indicating the transition width; c) the differential conductivity of the 32 nm sample at 300 K (black) and 365 K (red). (For interpretation of the references to colour in this figure legend, the reader is referred to the web version of this article.)

thickness (i.e. increase of the strain) is evident the increase of the Filling Ratio $F=(\pi^*+d_{||}^*)/\sigma^*$. Indeed, both π^* and $d_{||}^*$ are partially degenerate crossing the FL in the metallic phase. Considering that the σ^* contribution to the XANES spectra it is almost independent from the strain due to the stability of the σ bond, an increase of F , reveals an increase of the empty states with π^* and $d_{||}^*$ character. This implies a decrease of the number of occupied states and hence a decrease of free carriers in the most strained sample.

This demonstrates that the inversion in the π^* - $d_{||}^*$ orbital hierarchy is concurrent with a depletion of the FL population in the metallic phase of VO₂.

The FL filling dynamic as a function of sample thickness clearly points out that the MIT is of the FC type, suggesting the purely electronic character of a transition dominated by the short-ranged electron correlation rather than the electron-lattice coupling [37].

Regarding the spectral difference of the NS film, in Fig. 2 it is evident the negative contribution whose minimum is aligned with the strained samples. Going from the low temperature to the high-temperature phase, an increase of the intensity in the energy region of the t_{2g}^* is observed, pointing out that the main spectral changes across the MIT affect the empty orbitals with t_{2g} character.

To study the effect of strain over the electronic structure of VO₂ a set of ResPES measurements have been also performed exploring the photon energy through the V L₃ edge. Spectra of the 8, 16, 32 nm

samples and of the disordered NS sample in the $-2; 3$ eV Binding Energy (BE) region collected at the maximum of the V L₃ resonance are compared in Fig. 3.

For the entire set of samples, spectra of the metallic state are characterized by the population at the FL and are comparable with previously published data for VO₂ thin films [25]. The maximum of the $3d$ signal enhancement is observed at 518.4 ± 0.1 eV, in agreement with the maximum of the XANES V L edge spectrum [34], confirming once more the $3d$ nature of the 1–2 eV peak.

We used ResPES as a probe of the metallicity (i.e. the ability to screen an electric field) in our set of samples [52-54]. The maximum intensity (normalized to the photon flux) of resonant photoemission feature can be linked to the screening parameter by the Eq. (2) [52-54]

$$\frac{I}{I_0} \propto \frac{1}{L_s} \quad (2)$$

where I is the ResPES peak intensity, I_0 the incident photon flux and L_s the screening parameter of the material (the inverse of the Thomas-Fermi screening length [54]). In this framework, in an insulating material, (small L_s), the core-hole generated by the ResPES process is poorly screened allowing the resonantly excited state to decay in order to interfere with the direct photoemission. On the other hand, the delocalized electrons inside a metal (high L_s) quickly screen the photo-hole partially quenching the valence-to-core decay of the excited state

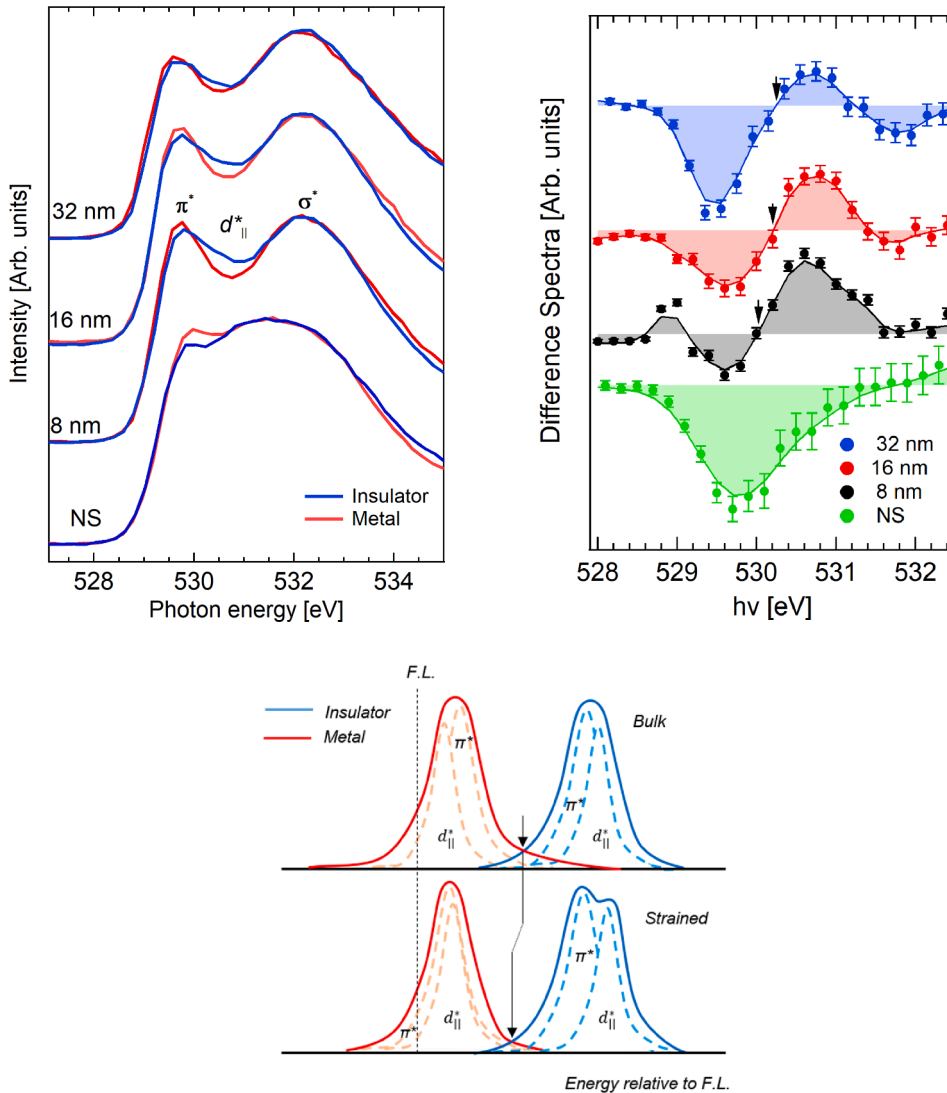


Fig. 2. Left panel: comparison of the O K edge XANES (527–535 eV) of VO₂ crystalline film of 32, 16 and 8 nm and the NS disordered film for metallic (red, 90° C) and insulating (blue, 30° C) phases. XANES spectra of the strained films are normalized respect to the maximum intensity of the σ^* feature at 532.2 eV; the spectra of the NS disordered films are normalized to the maximum of the intensity around the σ^* energy region: $h\nu = 531.6$ eV. Right panel: comparison of the difference spectra of the O K edge XANES in the range $h\nu: 528$ –532 eV. The dots represent experimental points while the continuous line (a guide for the eye) is the smoothed curve of the experimental points (binomial algorithm). From top to bottom: films of 32, 16 and 8 nm and the NS film. The black vertical arrows indicate the turning point of the difference from negative to positive contributions. Spectra are vertically shifted for sake of clarity. Bottom panel: the schematic empty band model for bulk and strained VO₂ in the insulator (blue) and metal (red) phases. The intersection point (marked by arrows) between the insulator and metal empty DOS shifts toward lower energy for the strained sample, because of the concurrent π^* , $d_{||}^*$ separation in the insulating phase and π^* , $d_{||}^*$ inversion in the metallic phase. (For interpretation of the references to colour in this figure legend, the reader is referred to the web version of this article.)

($2p^53d^2$ for L_3 resonant photoemission in VO_2), reducing the enhancement of the resonant signal.

When the excitation energy $h\nu$ is set at the maximum of the vanadium L_3 threshold, the insulating $3d$ peak is always more intense respect to the metallic counterpart as observable in Fig. 3. It is observable that while the strained films exhibit an intense signal at FL and therefore a pronounced metallicity, the NS disordered film shows a weak increase in the FL population. This can be explained considering that in the NS disordered film the lack of long range order inhibits the formation of the $d_{||}^*$ band which is the main source of available states at FL favouring the localization of $3d$ electron on V sites. The details of the FL population mechanism in the NS disordered film will be discussed further in the text.

Applying Eq. (2) to our dataset, we may calculate the ratio between the insulating and the metal phase ResPES intensity obtaining L_m/L_i (the ratio of the screening parameters of the metallic and insulating phases) as a function of the sample thickness (Fig. 4). The L_m/L_i values extracted are: 1.93, 1.73 and 1.44 for the 32, 16 and 8 nm samples respectively.

L_m/L_i can be estimated considering that the screening parameter is the inverse of the Debye screening length:

$$L_s = \frac{1}{\lambda_D} = \sqrt{\frac{e^2 n}{\epsilon k_b T}} \quad (3)$$

where λ_D is the Debye screening length, e is the carrier charge, n is the carrier density, $\epsilon = \epsilon_0 \epsilon_r$ is the average dielectric constant, k_b the Boltzmann constant and T the temperature. Therefore the ratio of the screening parameter of the metallic to insulator phase is:

$$\frac{L_m}{L_i} = \sqrt{\frac{n_m \epsilon_i T_i}{n_i \epsilon_m T_m}} \quad (4)$$

where the subscript m indicate the quantity relative to the metallic phase and i those relative to the insulating phase. Using the values of the dielectric constant reported by Zheng and coworkers [55] ($\epsilon_i = 40$ and $\epsilon_m = 10^4$) and the carrier concentration $n_i = 1.9 \cdot 10^{19} \text{cm}^{-3}$ $n_m = 1.9 \cdot 10^{23} \text{cm}^{-3}$ [56], with temperature $T_i = 303.15 \text{ K}$ and $T_m = 363.15 \text{ K}$

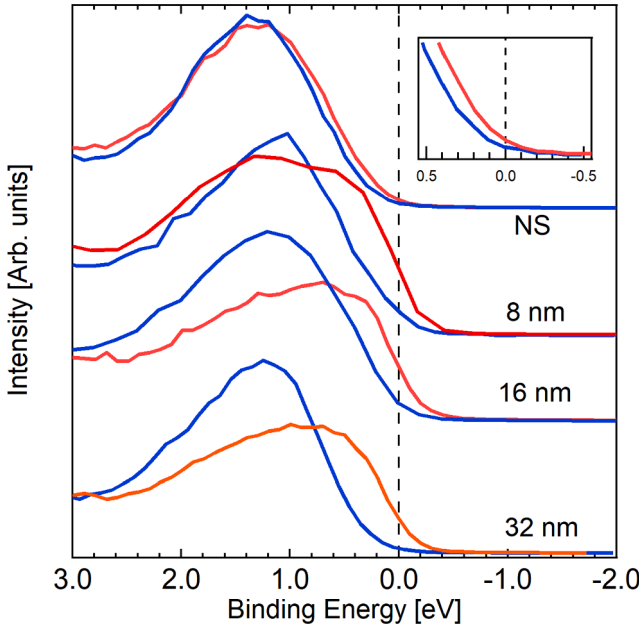


Fig. 3. VB spectra of the unpaired $3d$ electrons band in the BE range (-2; 3) eV in the insulating (blue) and metallic (red) phase of VO_2 . From top to bottom: the NS disordered sample, samples 8, 16 and 32 nm thick. The inset shows the increase of the population at the FL for the NS sample. (For interpretation of the references to colour in this figure legend, the reader is referred to the web version of this article.)

we obtain $L_m/L_i \approx 5.7$ for bulk VO_2 .

This value is not consistent with the measured $L_m/L_i = 1.93$ obtained for the 32 nm thick, bulk-like samples. This is mainly due because the Debye model cannot properly evaluate L_m . In fact, it is necessary to consider that the conductive phase of VO_2 is a “poor” metal in which electron correlation effects drive the transport properties. Indeed, metallic vanadium dioxide violates the Ioffe-Regel-Mott criterion [57], or in other words, the Boltzmann statistic cannot be used to describe VO_2 properties and therefore the Eq. (4) is a poor approximation of the metallic screening. Nevertheless, the Debye model allows to link the screening parameters ratio L_m/L_i to the carrier density of the metallic phase n_m , allowing us to interpret its thickness dependent variation as mainly due to the concurrent variation of the carrier density in the metallic phase.

In Fig. 4 we show the trend of L_m/L_i (blue dots) as a function of the sample thickness vs. F , the Filling ratio. L_m/L_i and F have opposite behaviors thus confirming the previous interpretation. In the metallic phase the strain affects the population at the FL, which is depleted respect to the bulk, i.e., F is higher in the most strained sample. Concurrently, due to the lack of itinerant electrons the screening parameter decreases in the strained samples. In other words, decreasing FL population, increases the spectral weight of the empty DOS (increase of F), this transfer of spectral weight is an additional fingerprint of the FC nature of the MIT in VO_2 [37].

This result combined with the XANES analysis, unambiguously links the strain-induced orbital hierarchy inversion in the metallic phase of VO_2 , with the variation of population at the FL and the metallicity, determining the FC nature of the MIT, i.e., driven by the electron correlation.

In the limiting case of the NS sample the appearance of a small, but finite DOS at the FL in the high-temperature spectra of the VB (inset of Fig. 3) points out the increase of the metallicity from 303.15 to 363.15 K, in agreement also with the value of the ratio $L_{\text{metal}}/L_{\text{insulator}} > 1$ (see Supplementary materials). In order to rule out a purely thermal mechanism for the modulation of the population at the FL, resistance measurements have been performed (Figure S2 in supplementary materials). As shown in Fig. 5 the temperature dependence of the resistance does not obey the Arrhenius law [58] and, since the Peierls mechanism is quenched by disorder, the electron-electron interaction is the only possible mechanism responsible of the change of the population at the FL.

A straightforward proof of the purely electronic character of MIT in NS VO_2 film is achieved through Constant Initial State (CIS) spectroscopy. CIS is an advanced spectroscopy technique, in which the modulation of the intensity of a photoemission feature is recorded as a

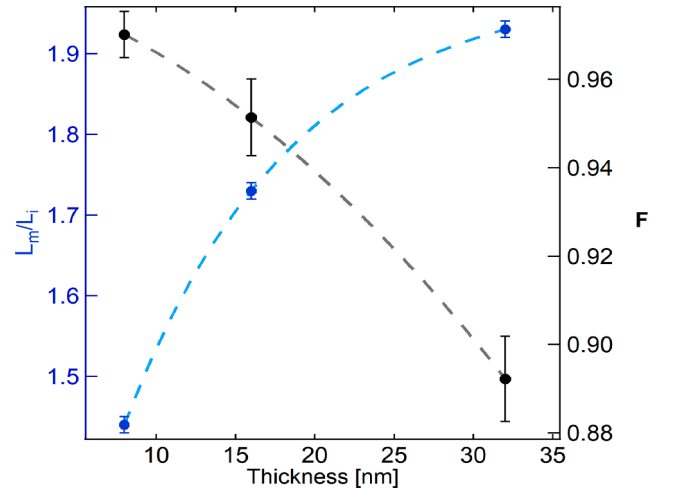


Fig. 4. Ratio of the ResPES intensity in the two phase: L_m/L_i (left axis) and the Filling ratio $F = (\pi^* + d_{||}^*) / \sigma^*$ (right axis) as a function of the sample thickness.

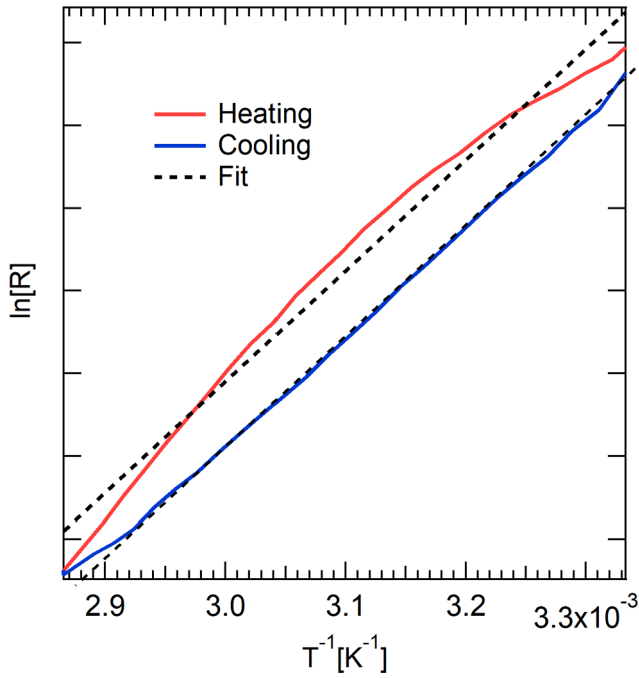


Fig. 5. The Arrhenius plot of the resistance of the NS disordered sample in the temperature range 300–350 K. Experimental data deviate from the theoretical linear dependence (broken black line).

function of the photon energy [42,43,59]. Respect to XANES, CIS spectroscopy is highly selective. In a CIS spectrum the photon energy and the kinetic energy of the electron are simultaneously varied to fulfil the condition with the ionization energy (E_i) as a constant.

$$E_i = h\nu - E_{KE} \quad (5)$$

Since E_i (or BE) is fixed, CIS measures the cross section ResPES lineshape mapping only the empty DOS region, which allows a resonant decay channel in a final state with a hole at the chosen E_i .

Across the phase transition of VO_2 the major spectral changes happen around FL.

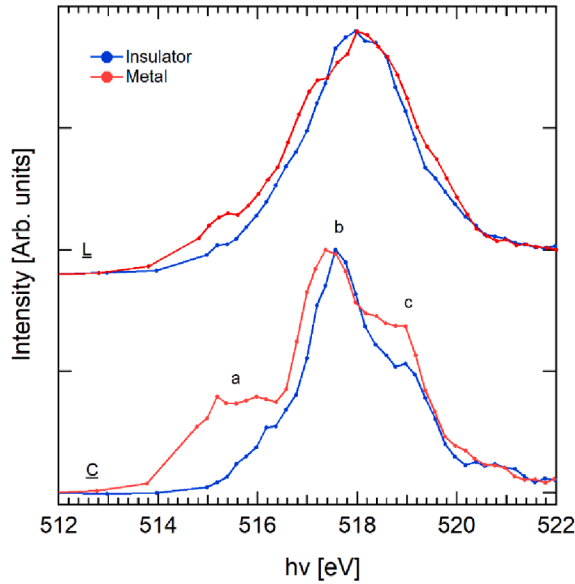


Fig. 6. Left panel, V 3d CIS spectra for \underline{L} (BE = 1.5 eV) and \underline{C} feature (BE = 0.4 eV) in the metallic (red) and insulating (blue) phase of the disordered NS sample. Spectra are normalized to the incident photon flux and to their maximum intensity. Right panel, schematic representation of the band evolution across the MIT in a disordered sample. The d_u band, originated by unpaired 3d electrons, in the insulating phase splits in d_u and d_u^* bands by electron–electron repulsion. Across the phase transition d_u^* collapses, crossing the Fermi energy and closing the band gap. (For interpretation of the references to colour in this figure legend, the reader is referred to the web version of this article.)

As observable in Fig. 3 (and supplementary materials) in the metallic phase, the valence band line-shape in the 0–3 eV range, is determined by the contribution of two features centered at about ~ 1.5 and ~ 0.5 eV. The presence of two contributions near the Fermi level is the result of the strong electron–electron interaction (U) in Mott-Hubbard metals [60]. For historical reasons, the low BE feature has been called coherent (or quasi-particle) peak since it is obtained by band structure calculations in the framework of the independent particle approximation, neglecting the many-body effects, while the high BE feature is named incoherent peak [60].

The coherent peak is generated by delocalized 3d band states. The quasi-particle and the incoherent peak can be assigned to two different final states in which two screening mechanisms operate. After the photoemission of a 3d electron, from the initial state with a formal $3d^1$ configuration the system goes in a $3d^0$ final state. According to Mossaneh and Abbate, the $3d^0$ configuration is poorly screened by the surrounding atoms while features near the Fermi Level are well-screened configurations [61]. In the VO_2 metallic phase, the most favorable final configurations are $3d^1\underline{C}$ (coherent hole) and $3d^1\underline{L}$ (ligand hole)[61]. The \underline{C} state accounts for a non-local screening channel of the photo-hole provided by the surrounding vanadium atoms. In the \underline{L} configuration, the nearest oxygen atoms provide the charge to screen the missing electron. According to theoretical calculations, we assigned to the $3d^1\underline{L}$ configuration the insulating phase peak around 1.2 eV of BE while the 0.5 eV feature has $3d^1\underline{C}$ nature [25,61].

Considering this, we studied the CIS spectra of the V 3d \underline{C} and \underline{L} features which are reported in Fig. 6. The spectra have been acquired spanning the photon energy across the V L_3 resonance.

The \underline{L} CIS spectra strongly resemble the V L_3 XANES spectrum [47]. Minor spectral changes are observed across the phase transition at $h\nu \sim 515$ eV. This is not surprising since the \underline{L} photoemission feature is connected with the local screening channel, i.e., is associated to well localized electrons. As a consequence since mostly V 3d - O 2p hybridized electrons are involved no major spectral changes across the MIT are expected.

On the other hand, the \underline{C} photoemission feature is intrinsically linked to the conductive phase of VO_2 . \underline{C} CIS spectra select the excited states, i. e., the empty DOS region, for which the V 3d photo-hole is well screened by the delocalized metallic channel. In other words \underline{C} CIS is sensitive to

the empty DOS region, which contributes to the metallic phase of the VO₂. Three main features can be recognized: *a* (~515 eV), *b* (~517.6 eV) and *c* (~519 eV). The e_g* character can be assigned to the high-energy *c* feature while the t_{2g}* to the *b* feature. The *a* feature nature deserves a deeper discussion because while it is evident in the spectrum of the conductive phase, its presence can be only associated to the shoulder around 516 eV in the low temperature CIS spectrum.

The appearance of the *a* feature is accompanied by the increase of the *c* intensity. Since CIS spectra are normalized to the maximum of the *b* feature, any spectral change has to be read as a transfer of the spectral weight from *b* to *a*. As a consequence, the *a* feature can be interpreted as of one of the t_{2g} empty orbitals not degenerate with the other two (*b* feature). The fact that *a* collapses toward low energy in the metallic phase while is partially degenerate with the t_{2g}* features in the insulating phase is the evidence of the *d*-band splitting across the MIT. Actually, the *a* feature in the CIS spectra can be associated to the d_u* band in the model in Fig. 6 (right panel).

Since the Peierls distortion in the NS sample is quenched, in this case, the insulator to metal transition can only be driven by the electron–electron interaction and correlation [18,23] allowing us to determine the orbital evolution across the MIT in a disordered VO₂ system.

The behaviour in the disordered NS sample confirms the electronic nature of the MIT and strengthens our interpretation of a MIT driven by electron–electron interaction and of the FC type, substantially independent by the lattice degree of freedom.

An additional phenomenology of a FC transition is the occurrence of, charge ordering (CO) phases. CO can arise in a 3d^{*n*} system when the filling number *n* is not integer [37]. Our study demonstrate that strain can be used to reduce the number of itinerant electrons, thus *n*, setting the necessary conditions for the emergence of CO in VO₂.

C. N. Singh and co-worker recently reported CO phenomena in VO₂/TiO₂ thin films [62], strengthening our interpretation of the FC nature of the MIT.

4. Conclusions

This study demonstrates that short-ranged electron interaction is the decisive parameter behind VO₂ MIT. The application of strain emerges as an invaluable tool to finely tune FL occupancy and metallicity in the metallic phase of VO₂.

Our spectroscopic analysis on strained and disordered samples, indicate that the MIT is of the FC type, therefore mostly independent from electron-lattice coupling. The identification of strain as a control parameter for band filling and occupation is of paramount importance since it can be used instead of solid state solutions or doping as the key to control the VO₂ MIT.

The role of strain over electron–electron interaction will enable the design of ultra-thin electronic devices with controllable electronic properties, such as band occupancy, based on the MIT, boosting the emerging field of Motronics for efficient new generation devices. In addition, the discovery of strain as control parameter of FL occupancy and therefore of electron correlation, is likely to be influential also in transversal hot topic fields such as that of ultra-thin perovskite films.

CRedit authorship contribution statement

A. D’Elia: Conceptualization, Methodology, Formal analysis, Investigation, Data curation, Writing - original draft, Writing - review & editing, Visualization. **C. Grazioli:** Investigation, Writing - review & editing. **A. Cossaro:** Investigation, Resources, Writing - review & editing. **B.W. Li:** Resources. **C.W. Zou:** Resources. **S.J. Rezvani:** Formal analysis, Investigation, Data curation, Writing - review & editing, Visualization. **N. Pinto:** Investigation, Writing - review & editing. **A. Marcelli:** Conceptualization, Investigation, Resources, Writing - review & editing. **M. Coreno:** Conceptualization, Funding acquisition.

Declaration of Competing Interest

The authors declare that they have no known competing financial interests or personal relationships that could have appeared to influence the work reported in this paper.

References

- [1] N. Pinto, S.J. Rezvani, L. Favre, I. Berbezier, M. Fretto, L. Boarino, Geometrically induced electron-electron interaction in semiconductor nanowires, *Appl. Phys. Lett.* 109 (2016), <https://doi.org/10.1063/1.4962893>.
- [2] S.J. Rezvani, R. Gunnella, D. Neilson, L. Boarino, L. Croin, G. Aprile, M. Fretto, P. Rizzi, D. Antonioli, N. Pinto, Effect of carrier tunneling on the structure of Si nanowires fabricated by metal assisted etching, *Nanotechnology*. (2016), <https://doi.org/10.1088/0957-4484/27/34/345301>.
- [3] S. Carturan, G. Maggioni, S.J. Rezvani, R. Gunnella, N. Pinto, M. Gelain, D. R. Napoli, Wet chemical treatments of high purity Ge crystals for γ -ray detectors: Surface structure, passivation capabilities and air stability, *Mater. Chem. Phys.* (2015), <https://doi.org/10.1016/j.matchemphys.2015.05.022>.
- [4] M. Pasqualini, S. Calcaterra, F. Maroni, S.J. Rezvani, A. Di Cicco, S. Alexander, H. Rajantie, R. Tossici, F. Nobili, Electrochemical and spectroscopic characterization of an alumina-coated LiMn2O4 cathode with enhanced interfacial stability, *Electrochim. Acta.* 258 (2017) 175–181, <https://doi.org/10.1016/j.electacta.2017.10.115>.
- [5] N.B. Aetukuri, A.X. Gray, M. Drouard, M. Cossale, L. Gao, A.H. Reid, R. Kukreja, H. Ohldag, C.A. Jenkins, E. Arenholz, K.P. Roche, H.A. Dürr, M.G. Samant, S.S. P. Parkin, Control of the metal-insulator transition in vanadium dioxide by modifying orbital occupancy, *Nat. Phys.* 9 (2013) 661–666, <https://doi.org/10.1038/nphys2733>.
- [6] J.M. Atkin, S. Berweger, E.K. Chavez, M.B. Raschke, J. Cao, W. Fan, J. Wu, Strain and temperature dependence of the insulating phases of VO₂ near the metal-insulator transition, *Phys. Rev. B - Condens. Matter Mater. Phys.* 85 (2012), 020101, <https://doi.org/10.1103/PhysRevB.85.020101>.
- [7] M. Yang, Y. Yang, B. Hong, L. Wang, K. Hu, Y. Dong, H. Xu, H. Huang, J. Zhao, H. Chen, L. Song, H. Ju, J. Zhu, J. Bao, X. Li, Y. Gu, T. Yang, X. Gao, Z. Luo, C. Gao, Suppression of Structural Phase Transition in VO₂ by Epitaxial Strain in Vicinity of Metal-insulator Transition, *Sci. Rep.* 6 (2016), <https://doi.org/10.1038/srep23119>.
- [8] Y. Tokura, Metal-insulator phenomena in perovskites of transition metal oxide, *Phys. B Condens. Matter.* 237–238 (1997) 1–5, [https://doi.org/10.1016/S0921-4526\(97\)00009-4](https://doi.org/10.1016/S0921-4526(97)00009-4).
- [9] C. Zhang, S. Ke, Y. Nie, C. Liang, W.G. Vandenberghe, R.C. Longo, Y. Zheng, F. Kong, S. Hong, R.M. Wallace, K. Cho, Charge Mediated Reversible Metal-Insulator Transition in Monolayer MoTe₂ and WxMo1-xTe2 Alloy, *ACS Nano*. (2016), <https://doi.org/10.1021/acsnano.6b00148>.
- [10] D. Meyers, J. Liu, J.W. Freeland, S. Middey, M. Kareev, J. Kwon, J.M. Zuo, Y. De Chuang, J.W. Kim, P.J. Ryan, J. Chakhalian, Pure electronic metal-insulator transition at the interface of complex oxides, *Sci. Rep.* (2016), <https://doi.org/10.1038/srep27934>.
- [11] F.J. Morin, Oxides which show a metal-to-insulator transition at the neel temperature, *Phys. Rev. Lett.* 3 (1959) 34–36, <https://doi.org/10.1103/PhysRevLett.3.34>.
- [12] J.B. Goodenough, The two components of the crystallographic transition in VO₂, *J. Solid State Chem.* 3 (1971) 490–500, [https://doi.org/10.1016/0022-4596\(71\)90091-0](https://doi.org/10.1016/0022-4596(71)90091-0).
- [13] Y. Cui, Y. Ke, C. Liu, Z. Chen, N. Wang, L. Zhang, Y. Zhou, S. Wang, Y. Gao, Y. Long, Thermochromic VO₂ for Energy-Efficient Smart Windows, *Joule.* 2 (2018) 1707–1746, <https://doi.org/10.1016/j.joule.2018.06.018>.
- [14] M. Brahlek, L. Zhang, J. Lapano, H.T. Zhang, R. Engel-Herbert, N. Shukla, S. Datta, H. Paik, D.G. Schlom, Opportunities in vanadium-based strongly correlated electron systems, *MRS Commun.* 7 (2017) 27–52, <https://doi.org/10.1557/mrc.2017.2>.
- [15] T. Yajima, T. Nishimura, A. Toriumi, Positive-bias gate-controlled metal-insulator transition in ultrathin VO₂ channels with TiO₂ gate dielectrics, *Nat. Commun.* 6 (2015), <https://doi.org/10.1038/ncomms10104>.
- [16] A. Zylbersztejn, N.F. Mott, Metal-insulator transition in vanadium dioxide, *Phys. Rev. B.* 11 (1975) 4383–4395, <https://doi.org/10.1103/PhysRevB.11.4383>.
- [17] F. Grandi, A. Amaricci, M. Fabrizio, Unraveling the Mott-Peierls intrigue in vanadium dioxide, *Phys. Rev. Res.* (2020), <https://doi.org/10.1103/physrevresearch.2.013298>.
- [18] C. Weber, D.D. O’Regan, N.D.M. Hine, M.C. Payne, G. Kotliar, P.B. Littlewood, Vanadium Dioxide: A Peierls-Mott Insulator Stable against Disorder, *Phys. Rev. Lett.* 108 (2012), 256402, <https://doi.org/10.1103/PhysRevLett.108.256402>.
- [19] A. Moatti, R. Sachan, V.R. Cooper, J. Narayan, Electrical Transition in Isostructural VO₂ Thin-Film Heterostructures, *Sci. Rep.* 9 (2019), <https://doi.org/10.1038/s41598-019-39529-z>.

- [20] B.S. Mun, J. Yoon, S.K. Mo, K. Chen, N. Tamura, C. Dejoie, M. Kunz, Z. Liu, Y. Yvette Lee, K. Moon, C. Park, H. Ju, Metal insulator transition characteristics of macro-size single domain VO₂ crystals, *Phase Transitions*. 86 (2013) 941–946, <https://doi.org/10.1080/01411594.2012.717291>.
- [21] L.L. Fan, S. Chen, Z.L. Luo, Q.H. Liu, Y.F. Wu, L. Song, D.X. Ji, P. Wang, W.S. Chu, C. Gao, C.W. Zou, Z.Y. Wu, Strain dynamics of ultrathin VO₂ film grown on TiO₂ (001) and the associated phase transition modulation, *Nano Lett.* 14 (2014) 4036–4043, <https://doi.org/10.1021/nl501480f>.
- [22] A. Cavalleri, T. Dekorsy, H.H.W. Chong, J.C. Kieffer, R.W. Schoenlein, Evidence for a structurally-driven insulator-to-metal transition in VO₂: A view from the ultrafast timescale, *Phys. Rev. B*. 70 (2004), 161102, <https://doi.org/10.1103/PhysRevB.70.161102>.
- [23] V.R. Morrison, R.P. Chatelain, K.L. Tiwari, A. Hendaoui, A. Bruhács, M. Chaker, B. J. Siwick, A photoinduced metal-like phase of monoclinic VO₂ revealed by ultrafast electron diffraction, *Science* (80-). 346 (2014) 445–448. doi:10.1126/science.1253779.
- [24] R. Zimmermann, R. Claessen, F. Reinert, P. Steiner, S. Hüfner, Strong hybridization in vanadium oxides: Evidence from photoemission and absorption spectroscopy, *J. Phys. Condens. Matter*. 10 (1998) 5697–5716, <https://doi.org/10.1088/0953-8984/10/25/018>.
- [25] R. Eguchi, M. Taguchi, M. Matsunami, K. Horiba, K. Yamamoto, Y. Ishida, A. Chainani, Y. Takata, M. Yabashi, D. Miwa, Y. Nishino, K. Tamasaku, T. Ishikawa, Y. Senba, H. Ohashi, Y. Murakoa, Z. Hiroi, S. Shin, Photoemission evidence for a Mott-Hubbard metal-insulator transition in VO₂, *Phys. Rev. B - Condens. Matter Mater. Phys.* 78 (2008), 075115, <https://doi.org/10.1103/PhysRevB.78.075115>.
- [26] S. Suga, A. Sekiyama, S. Imada, T. Miyamachi, H. Fujiwara, A. Yamasaki, K. Yoshimura, K. Okada, M. Yabashi, K. Tamasaku, A. Higashiya, T. Ishikawa, –8 keV photoemission of the metal-insulator transition system VO₂, *New J. Phys.* 11 (2009), <https://doi.org/10.1088/1367-2630/11/10/103015>.
- [27] M.W. Haverkort, Z. Hu, A. Tanaka, W. Reichelt, S.V. Streltsov, M.A. Korotin, V. I. Anisimov, H.H. Hsieh, H.J. Lin, C.T. Chen, D.I. Khomskii, L.H. Tjeng, Orbital-assisted metal-insulator transition in VO₂, *Phys. Rev. Lett.* 95 (2005), <https://doi.org/10.1103/PhysRevLett.95.196404>.
- [28] J. Narayan, V.M. Bhosle, Phase transition and critical issues in structure-property correlations of vanadium oxide, *J. Appl. Phys.* 100 (2006), 103524, <https://doi.org/10.1063/1.2384798>.
- [29] A.X. Gray, M.C. Hoffmann, J. Jeong, N.P. Aetukuri, D. Zhu, H.Y. Hwang, N. C. Brandt, H. Wen, A.J. Sternbach, S. Bonetti, A.H. Reid, R. Kukreja, C. Graves, T. Wang, P. Granitzka, Z. Chen, D.J. Hgley, T. Chase, E. Jal, E. Abreu, M.K. Liu, T.-C. Weng, D. Sokaras, D. Nordlund, M. Chollet, R. Alonso-Mori, H. Lemke, J. M. Glownia, M. Trigo, Y. Zhu, H. Ohldag, J.W. Freeland, M.G. Samant, J. Berakdar, R.D. Averitt, K.A. Nelson, S.S.P. Parkin, H.A. Dürr, Ultrafast terahertz field control of electronic and structural interactions in vanadium dioxide, *Phys. Rev. B*. 98 (2018), 045104, <https://doi.org/10.1103/PhysRevB.98.045104>.
- [30] D. Lee, B. Chung, Y. Shi, G.Y. Kim, N. Campbell, F. Xue, K. Song, S.Y. Choi, J.P. Podkaminer, T.H. Kim, P.J. Ryan, J.W. Kim, T.R. Paudel, J.H. Kang, J.W. Spinuzzi, D.A. Tenne, E.Y. Tsybal, M.S. Rzechowski, L.Q. Chen, J. Lee, C.B. Eom, Isostructural metal-insulator transition in VO₂, *Science* (80-). 362 (2018) 1037–1040. doi:10.1126/science.aam9189.
- [31] S. Lee, K. Hippalgaonkar, F. Yang, J. Hong, C. Ko, J. Suh, K. Liu, K. Wang, J. Urban, X. Zhang, C. Dames, S.A. Hartnoll, O. Delaire, J. Wu, Anomalous low electronic thermal conductivity in metallic vanadium dioxide, *Science*. 355 (2017) 371–374, <https://doi.org/10.1126/science.aag0410>.
- [32] N.F. Quackenbush, J.W. Tashman, J.A. Mundy, S. Sallis, H. Paik, R. Misra, J. A. Moyer, J.H. Guo, D.A. Fischer, J.C. Woicik, D.A. Muller, D.G. Schlom, L.F. J. Piper, Nature of the metal insulator transition in ultrathin epitaxial vanadium dioxide, *Nano Lett.* 13 (2013) 4857–4861, <https://doi.org/10.1021/nl402716d>.
- [33] S. Mukherjee, N.F. Quackenbush, H. Paik, C. Schlueter, T.L. Lee, D.G. Schlom, L.F. J. Piper, W.C. Lee, Tuning a strain-induced orbital selective Mott transition in epitaxial VO₂, *Phys. Rev. B*. (2016), <https://doi.org/10.1103/PhysRevB.93.241110>.
- [34] A. D'Elia, S.J. Rezvani, A. Cossaro, M. Stredansky, C. Grazioli, B.W. Li, C.W. Zou, M. Coreno, A. Marcelli, Strain Induced Orbital Dynamics Across the Metal Insulator Transition in Thin VO₂/TiO₂ (001) Films, *J. Supercond. Nov. Magn.* 33 (2020) 2383–2388, <https://doi.org/10.1007/s10948-019-05378-0>.
- [35] W.C. Lee, M.J. Wahila, S. Mukherjee, C.N. Singh, T. Eustance, A. Regoutz, H. Paik, J.E. Boschker, F. Rodolakis, T.L. Lee, D.G. Schlom, L.F.J. Piper, Cooperative effects of strain and electron correlation in epitaxial VO₂ and NbO₂, *J. Appl. Phys.* (2019), <https://doi.org/10.1063/1.5052636>.
- [36] A. Bianconi, Multiplet splitting of final-state configurations in x-ray-absorption spectrum of metal VO₂: Effect of core-hole-screening, electron correlation, and metal-insulator transition, *Phys. Rev. B*. 26 (1982) 2741–2747, <https://doi.org/10.1103/PhysRevB.26.2741>.
- [37] M. Imada, A. Fujimori, Y. Tokura, Metal-insulator transitions, *Rev. Mod. Phys.* 70 (1998) 1039–1263, <https://doi.org/10.1103/RevModPhys.70.1039>.
- [38] L.L. Fan, S. Chen, Y.F. Wu, F.H. Chen, W.S. Chu, X. Chen, C.W. Zou, Z.Y. Wu, Growth and phase transition characteristics of pure M-phase VO₂ epitaxial film prepared by oxide molecular beam epitaxy, *Appl. Phys. Lett.* 103 (2013), <https://doi.org/10.1063/1.4823511>.
- [39] M. de Simone, E. Snidero, M. Coreno, G. Bongiorno, L. Giorgetti, M. Amati, C. Cepek, Oxidation of nanostructured Ti films produced by low energy cluster beam deposition: An X-ray Photoelectron Spectroscopy characterization, *Thin Solid Films*. 520 (2012) 4803–4807, <https://doi.org/10.1016/j.tsf.2011.10.075>.
- [40] A. D'Elia, C. Cepek, M. de Simone, S. Macis, B. Belec, M. Fanetti, P. Piseri, A. Marcelli, M. Coreno, Interplay among work function, electronic structure and stoichiometry in nanostructured VO_x films, *Phys. Chem. Chem. Phys.* 22 (2020) 6282–6290, <https://doi.org/10.1039/D0CP00216J>.
- [41] R. Costantini, M. Stredansky, D. Cvetko, G. Kladnik, A. Verdini, P. Sigalotti, F. Cilento, F. Salvador, A. De Luisa, D. Benedetti, L. Floreano, A. Morgante, A. Cossaro, M. Dell'Angela, ANCHOR-SUNDY: A novel endstation for time resolved spectroscopy at the ALOISA beamline, *J. Electron Spectros. Relat. Phenomena*. 229 (2018) 7–12, <https://doi.org/10.1016/j.elspec.2018.09.005>.
- [42] A. Marcelli, M. Coreno, M. Stredansky, W. Xu, C. Zou, L. Fan, W. Chu, S. Wei, A. Cossaro, A. Ricci, A. Bianconi, A. D'Elia, Nanoscale Phase Separation and Lattice Complexity in VO₂: The Metal-Insulator Transition Investigated by XANES via Auger Electron Yield at the Vanadium L23-Edge and Resonant Photoemission, *Condens. Matter*. 2 (2017) 38, <https://doi.org/10.3390/condmat2040038>.
- [43] R.Z. Bachrach, *Synchrotron Radiation Research Advances in Surface and Interface Science*, Springer, US, Boston MA, 1992, 10.1007/978-1-4615-3278-1.
- [44] N. Pinto, F. Caproli, G. Maggioni, S. Carturan, D.R. Napoli, Thermally induced irreversibility in the conductivity of germanium nitride and oxynitride films, *Mater. Sci. Semicond. Process.* 74 (2018) 57–63, <https://doi.org/10.1016/j.mssp.2017.10.006>.
- [45] N. Pinto, S.J. Rezvani, A. Perali, L. Flammia, M.V. Milošević, M. Fretto, C. Cassiagno, N. De Leo, Dimensional crossover and incipient quantum size effects in superconducting niobium nanofilms, *Sci. Rep.* 8 (2018), <https://doi.org/10.1038/s41598-018-22983-6>.
- [46] S. Lee, T.L. Meyer, C. Sohn, D. Lee, J. Nichols, D. Lee, S.S.A. Seo, J.W. Freeland, T. W. Noh, H.N. Lee, Electronic structure and insulating gap in epitaxial VO₂ polymorphs, *APL Mater.* 3 (2015), 126109, <https://doi.org/10.1063/1.4939004>.
- [47] A. D'Elia, S.J. Rezvani, N. Zema, F. Zuccaro, M. Fanetti, B. Belec, B.W. Li, C.W. Zou, C. Spezzani, M. Sacchi, A. Marcelli, M. Coreno, Tunable electronic structure and stoichiometry dependent disorder in Nanostructured VO_x films, (2020) 1–9. <https://arxiv.org/abs/2004.07042>.
- [48] M. Abbate, F.M.F. De Groot, J.C. Fuggle, Y.J. Ma, C.T. Chen, F. Sette, A. Fujimori, Y. Ueda, K. Kosuge, Soft-x-ray-absorption studies of the electronic-structure changes through the VO₂ phase transition, *Phys. Rev. B*. 43 (1991) 7263–7266, <https://doi.org/10.1103/PhysRevB.43.7263>.
- [49] D. Ruzmetov, S.D. Senanayake, S. Ramanathan, X-ray absorption spectroscopy of vanadium dioxide thin films across the phase-transition boundary, *Phys. Rev. B - Condens. Matter Mater. Phys.* 75 (2007), <https://doi.org/10.1103/PhysRevB.75.195102>.
- [50] S. Kasatkov, E. Filatova, S. Sakhonenkov, A. Konashuk, A. Makarova, Relationship between Ta Oxidation State and Its Local Atomic Coordination Symmetry in a Wide Range of Oxygen Nonstoichiometry Extent of TaO_x, *J. Phys. Chem. C*. 123 (2019) 6849–6860, <https://doi.org/10.1021/acs.jpcc.8b12053>.
- [51] M. Wu, J.C. Zheng, H.Q. Wang, Investigation of the vanadium L23 -edge x-ray absorption spectrum of SrVO₃ using configuration interaction calculations: Multiplet, valence, and crystal-field effects, *Phys. Rev. B*. 97 (2018), <https://doi.org/10.1103/PhysRevB.97.245138>.
- [52] P.A. Dowben, Metallicity of thin films and overlayers, *Surf. Sci. Rep.* 40 (2000) 151–247, [https://doi.org/10.1016/S0167-5729\(00\)00010-8](https://doi.org/10.1016/S0167-5729(00)00010-8).
- [53] D. McIlroy, C. Waldfried, J. Zhang, J.W. Choi, F. Foong, S. Liou, P. Dowben, Comparison of the temperature-dependent electronic structure of the perovskites), *Phys. Rev. B - Condens. Matter Mater. Phys.* 54 (1996) 17438–17451, <https://doi.org/10.1103/PhysRevB.54.17438>.
- [54] D. Li, J. Zhang, S. Lee, P.A. Dowben, Evidence for the formation of metallic mercury overlayers on Si(111), *Phys. Rev. B*. 45 (1992) 11876–11884, <https://doi.org/10.1103/PhysRevB.45.11876>.
- [55] Z. Yang, C. Ko, V. Balakrishnan, G. Gopalakrishnan, S. Ramanathan, Dielectric and carrier transport properties of vanadium dioxide thin films across the phase transition utilizing gated capacitor devices, *Phys. Rev. B - Condens. Matter Mater. Phys.* 82 (2010), <https://doi.org/10.1103/PhysRevB.82.205101>.
- [56] D. Fu, K. Liu, T. Tao, K. Lo, C. Cheng, B. Liu, R. Zhang, H.A. Bechtel, J. Wu, Comprehensive study of the metal-insulator transition in pulsed laser deposited epitaxial VO₂ thin films, *J. Appl. Phys.* 113 (2013), <https://doi.org/10.1063/1.4788804>.
- [57] M.M. Qazilbash, K.S. Burch, D. Whisler, D. Shrekhamer, B.G. Chae, H.T. Kim, D.N. Basov, Correlated metallic state of vanadium dioxide, *Phys. Rev. B - Condens. Matter Mater. Phys.* 74 (2006), <https://doi.org/10.1103/PhysRevB.74.205118>.
- [58] R. Bharathi, R. Naorem, A.M. Umarji, Metal-insulator transition characteristics of vanadium dioxide thin films synthesized by ultrasonic nebulized spray pyrolysis of an aqueous combustion mixture, *J. Phys. D. Appl. Phys.* 48 (2015), 305103, <https://doi.org/10.1088/0022-3727/48/30/305103>.
- [59] G.J. Lapeyre, R.J. Smith, J. Knapp, J. Anderson, Constant Final Energy and Constant Initial Energy Spectroscopy, *Le J. Phys. Colloq.* 39 (1978) C4-134-C4-141. doi:10.1051/jphyscol:1978417.
- [60] A. Fujimori, I. Hase, H. Namatame, Y. Fujishima, Y. Tokura, H. Eisaki, S. Uchida, K. Takegahara, F.M.F. De Groot, Evolution of the spectral function in Mott-Hubbard systems with d1 configuration, *Phys. Rev. Lett.* 69 (1992) 1796–1799, <https://doi.org/10.1103/PhysRevLett.69.1796>.
- [61] R.J.O. Mossaneck, M. Abbate, Cluster model calculations with nonlocal screening channels of metallic and insulating V O₂, *Phys. Rev. B - Condens. Matter Mater. Phys.* 74 (2006), <https://doi.org/10.1103/PhysRevB.74.125112>.
- [62] C.N. Singh, L.F.J. Piper, H. Paik, D.G. Schlom, W. Lee, Correlation induced emergent charge order in metallic vanadium dioxide, *ArXiv* (2020) 1–7.